

# MODIFICATION OF GRAPHENE OXIDE SURFACE BY DOPAMINE HYDROCHLORIDE

<sup>1,2</sup> Karel KLOUDA, <sup>2</sup>Petra ROUPCOVÁ, <sup>3</sup>Hana KUBÁTOVÁ, <sup>2</sup>Bohdan FILIPI, <sup>4</sup>David KRSEK, <sup>1</sup>Kateřina BÁTRLOVÁ

<sup>1</sup>Occupational Safety Research Institute, Prague, Czech Republic, EU, [kouda@vubr.cz](mailto:kouda@vubr.cz); [batrlova@vubr.cz](mailto:batrlova@vubr.cz)


<sup>2</sup>VSB - Technical University of Ostrava, Ostrava, Czech Republic, EU, [karel.kouda@vsb.cz](mailto:karel.kouda@vsb.cz); [petra.roupcova@vsb.cz](mailto:petra.roupcova@vsb.cz); [bohdan.filipi@vsb.cz](mailto:bohdan.filipi@vsb.cz)

<sup>3</sup>State Office for Nuclear Safety, Prague, Czech Republic, EU, [hana.kubatova@psuj.cz](mailto:hana.kubatova@psuj.cz)

<sup>4</sup>National Institute of Public Health, Prague, Czech Republic, EU, [krsek@zku.cz](mailto:krsek@zku.cz)


## INTRODUCTION

Dopamine (DA) is a biologically active substance from the catecholamine group. It is a neurotransmitter that is naturally produced in the nervous system of humans and animals. At the same time, it can be easily synthesized in large quantities. It is easy to prepare polydopamine (PDA) from dopamine and other catecholamines, [1, 2]. It is currently being studied in detail for its unique properties, which are very similar to the adhesive proteins of marine shells. Adhesive proteins allow mussels to interact with the substrate in moist environments, and they are rich in 3,4-dihydroxyphenylalanine (DOPA) as well as cysteine and lysine [1, 4]. The catechol side chain of DOPA is responsible for the strong bond between the surface of a bivalve leg and the substrate, as well as for the rapid solidification of the adhesive proteins. Catechol forms strong covalent and non-covalent interactions with the surface [5]. The synergistic effect of catechol and amine moiety further enhances biomolecular adhesion [1, 3]. These strong interactions with surfaces are also generated by PDA. Therefore, PDA is seen as an organic substance that is almost universally applicable to cover all kinds of materials. The thickness of the PDA layer can be influenced by the reaction conditions (reaction time, temperature, pH) [1, 5, 6]. Following PDA application, new functional groups (mainly hydroxyl or other, depending on the pH) appear on the surface of a material increasing its hydrophilicity. These functional groups can be subsequently used for further surface modifications [3]. PDA demonstrates considerable chemical and environmental stability [7]. Pyrolysis at temperatures around 800 °C produces a material with a graphene-like structure, where a nitrogen atom is irregularly embedded in the carbon skeleton. The obtained material is electrically conductive [1, 6]. PDA can be applied in many fields due to its potential to undergo further surface modifications and its ability to adhere to organic and inorganic substances. In biomedicine, for example, it is used to prepare nanocapsules for drug delivery or to reduce the immunogenicity of materials by improving their hydrophilicity and biocompatibility. PDA can be widely used in wastewater treatment to remove heavy metals, organic pollutants, dyes and radioactive isotopes. Our experiments focused specifically on the potential applications in water treatment. Graphene oxide (GO) and its hybrid compounds demonstrate sorption capabilities. It can be assumed that the reaction with DA will increase these abilities as a result of surface modification. Since we consider using both materials for sorption of organic pollutants present in water, it is necessary to have characteristics of both the input materials and of the materials with modified surfaces. For the pilot characterization we have chosen to use FTIR, TGA, DSC and microscopic methods (optical microscopy, TEM).

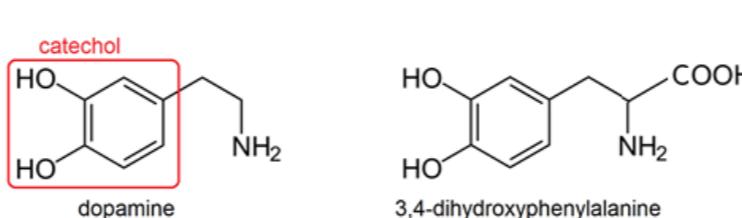

## 2. EXPERIMENTAL PART AND RESULTS

GO was prepared by oxidizing finely ground graphite (0.025 mm) according to the classical Hummers method (H<sub>2</sub>SO<sub>4</sub>, NaNO<sub>3</sub>, H<sub>2</sub>O<sub>2</sub>, KMnO<sub>4</sub>, HCl) [17]. The oxidation product was repeatedly centrifuged until a negative reaction to sulfate ions was obtained. The prepared GO (0.389 g) was subsequently used for the reaction with dopamine hydrochloride (0.309 g). PDA was synthesized via DA self-polymerization. The reaction was carried out in water (30 ml) with an addition of hydrogen peroxide (30%; 0.4 ml). The suspension was agitated for 19 h and the pH was adjusted to 8-9 using NaHCO<sub>3</sub>. The resulting suspension was washed with water and ethanol on a filter and then dried at 55 °C on a Petri dish. The hybrid compound GO-C<sub>60</sub> (3:1) was prepared by the simultaneous oxidation of graphite with fullerene C<sub>60</sub> in a weight ratio of 3:1. The procedure is described in Roupcová's dissertation. The obtained GO-C<sub>60</sub> (3:1) (0.350 g) was used for the reaction with dopamine hydrochloride (0.3 g). The reaction was carried out in water (30 ml) with an addition of hydrogen peroxide (30%; 0.4 ml) for 4 h. The pH was adjusted to 8-9 using NaHCO<sub>3</sub>. The obtained suspension was washed with water and ethanol on a filter and then dried at 55 °C on a Petri dish.

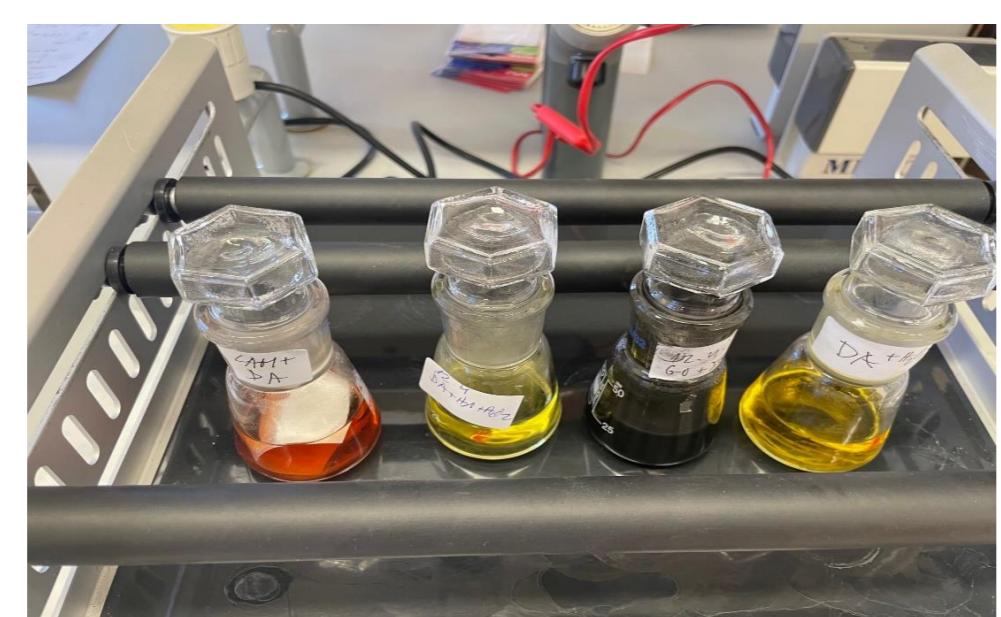

### 3.1 MORPHOLOGY

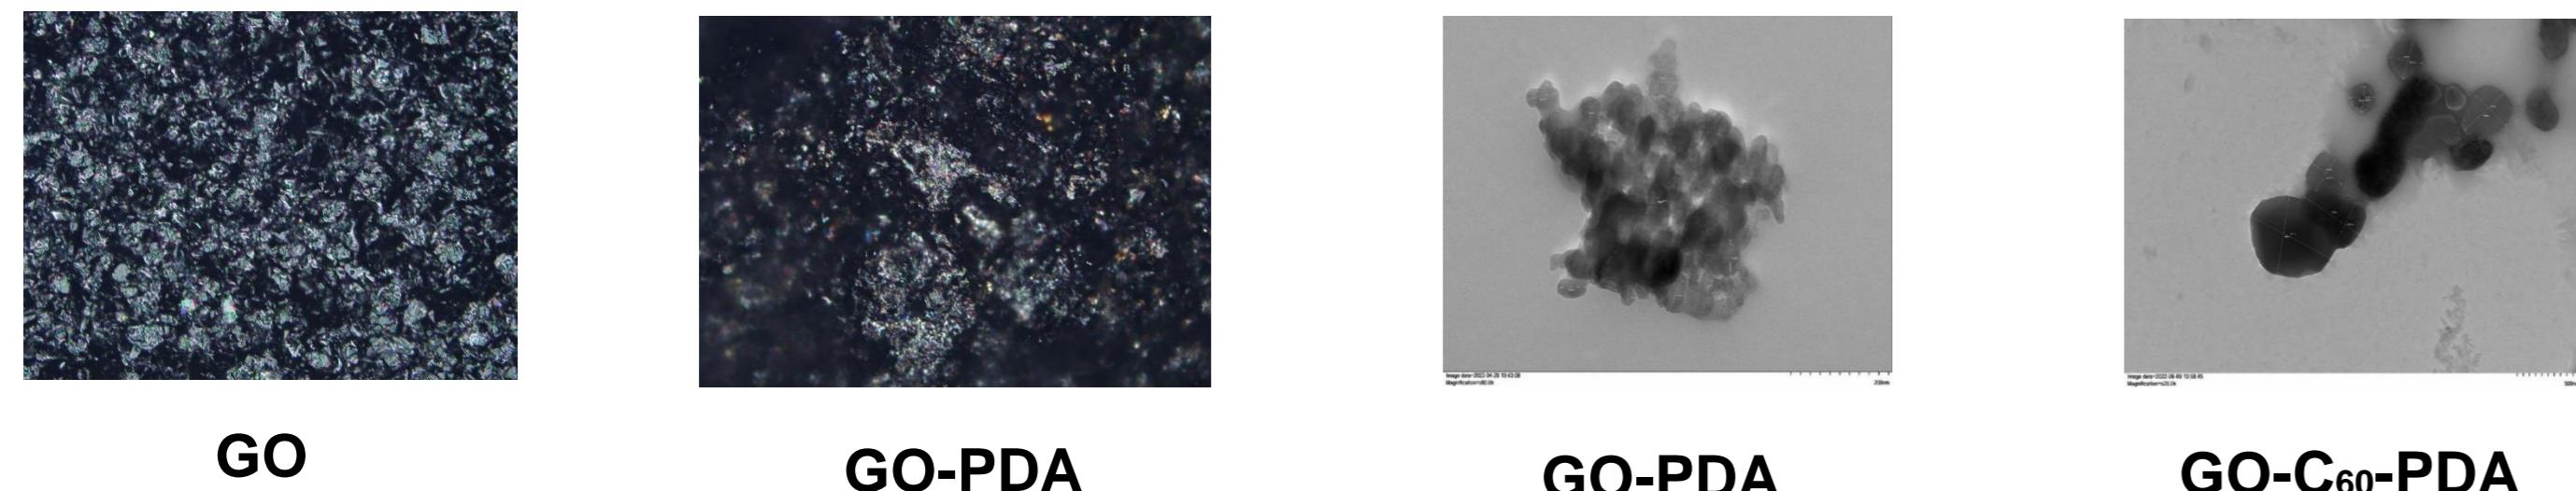


Figure 5 Microscopic images of the morphology of the initial GO (left) and the products of its reaction with DA (right) (magnification 20x)

Figure 6 Transmission electron microscopy (TEM) images of GO-PDA (left) and GO-C<sub>60</sub>-PDA (right)

## 3. CHARACTERIZATION OF MATERIALS BY FT-IR, AND BY TGA AND DSC ANALYSIS

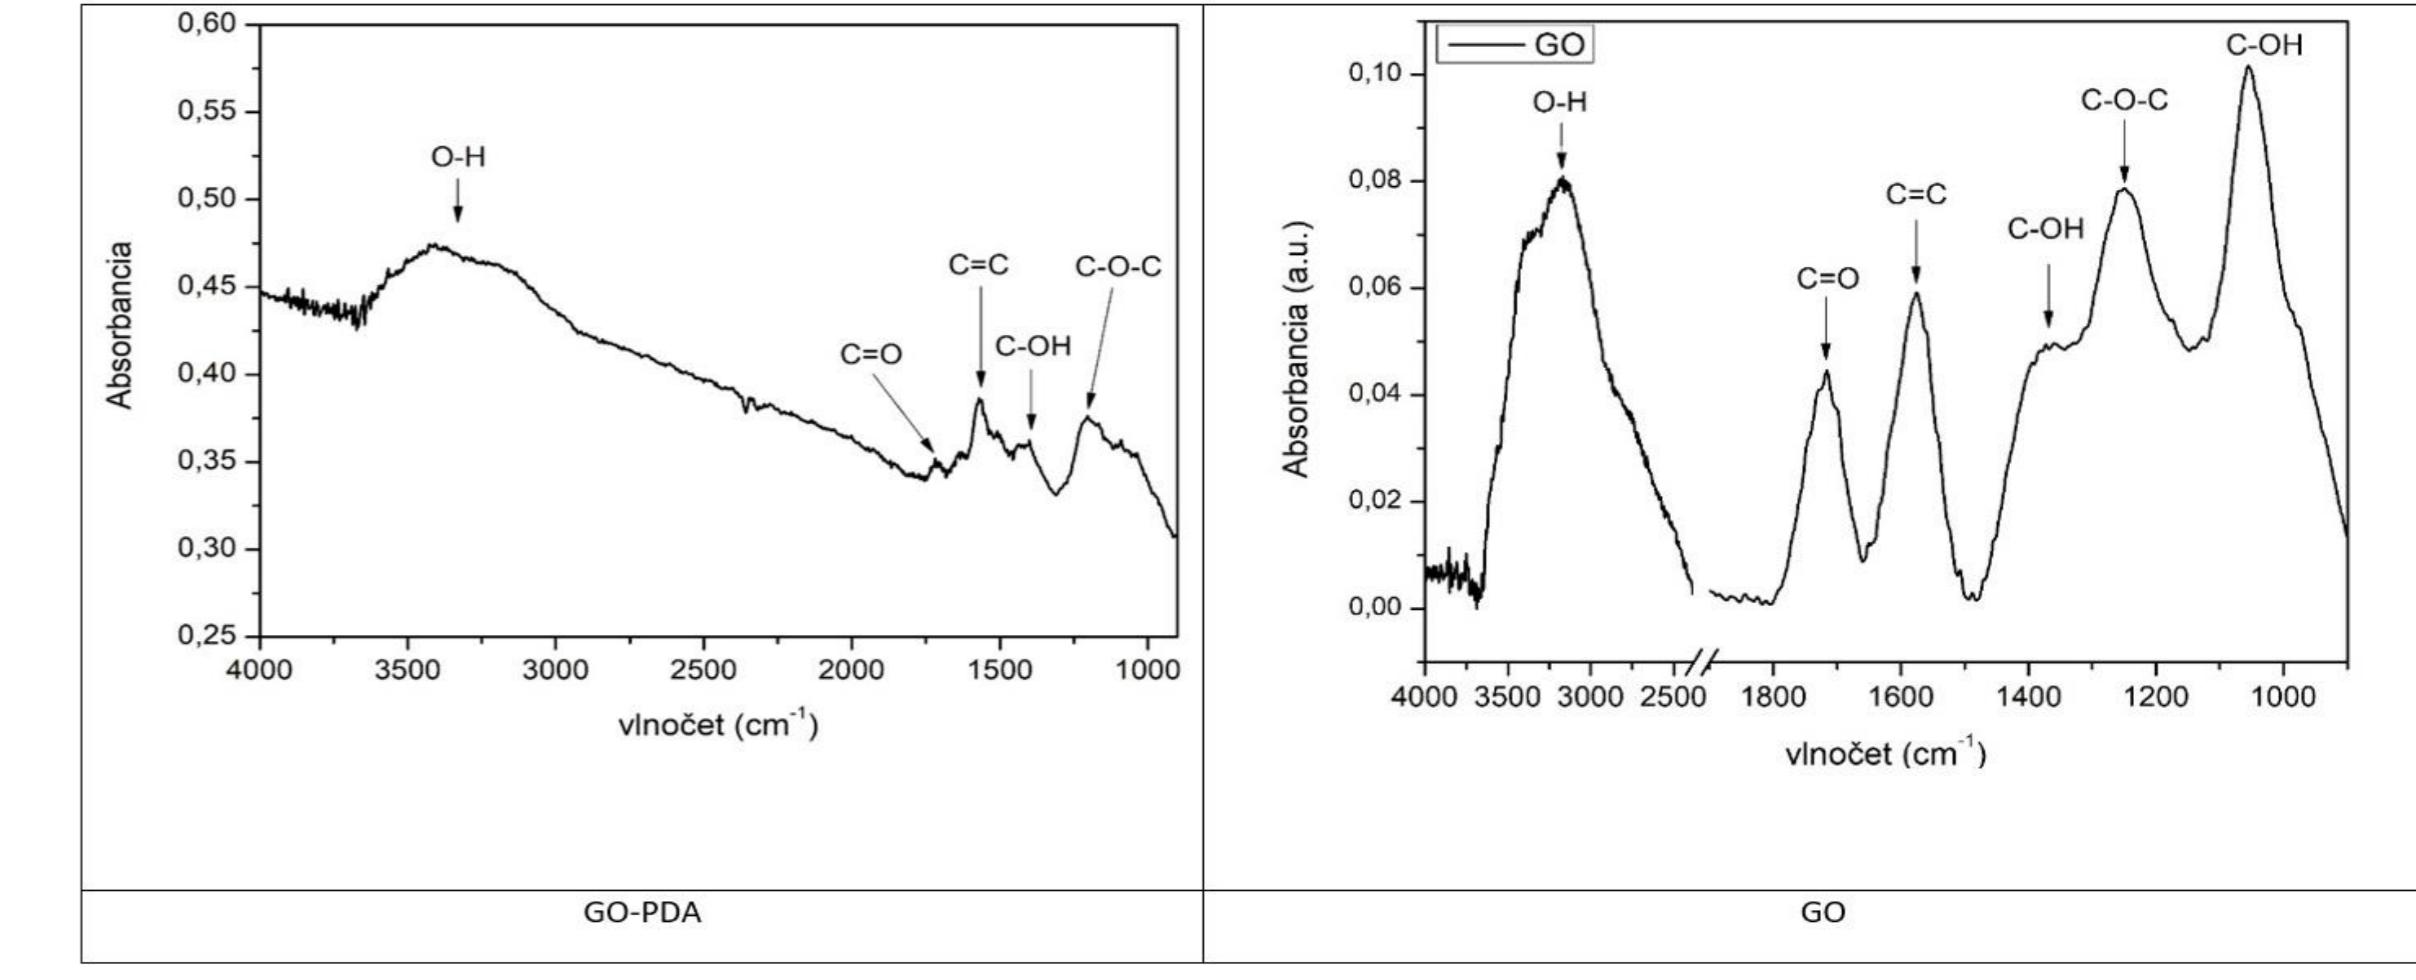


Figure 1 The FTIR spectra of GO and product formed on reaction of GO and PDA (GO-PDA)

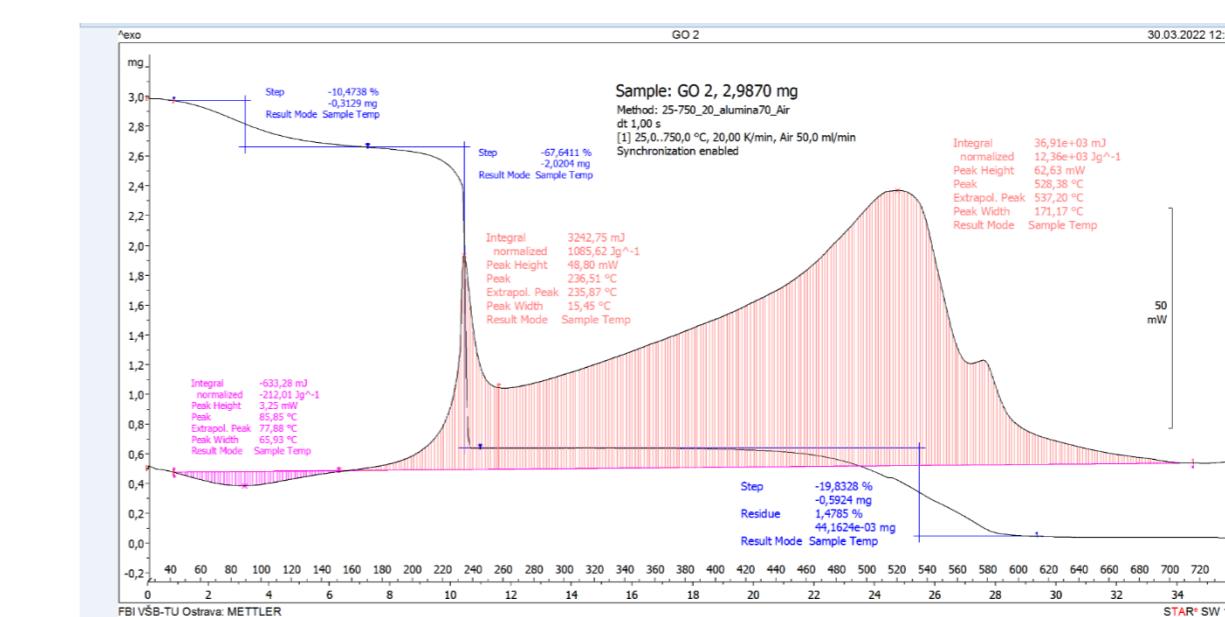


Figure 2 Thermal analysis data measured for GO (TGA/DSC curves)

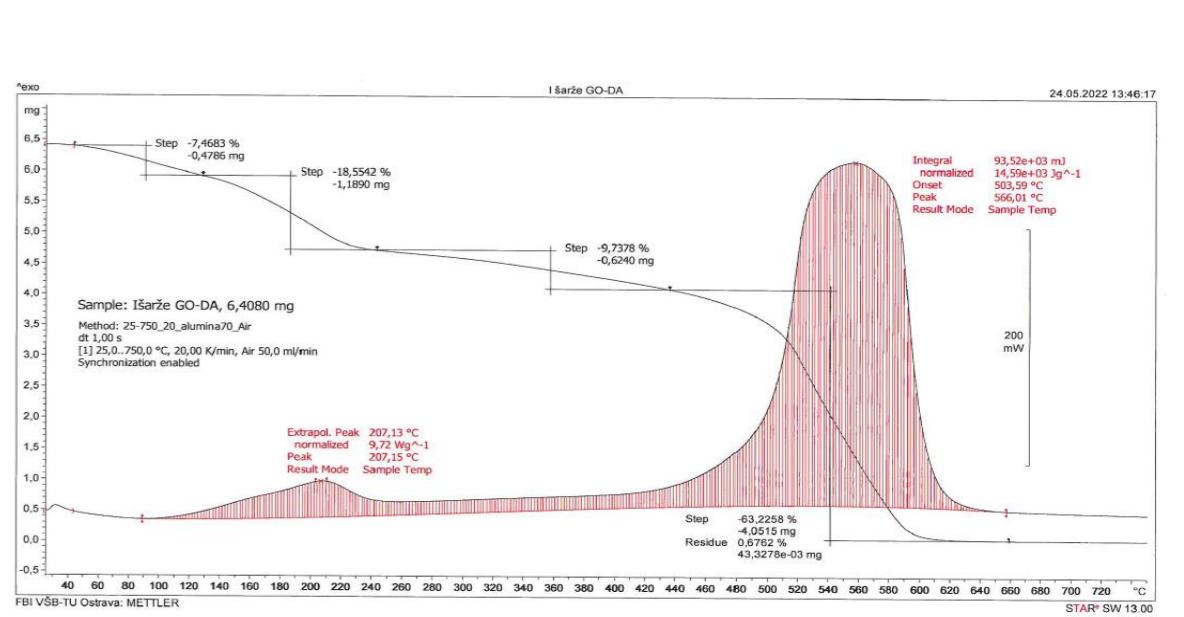


Figure 3 Thermal analysis data measured for GO-PDA (TGA/DSC curves)

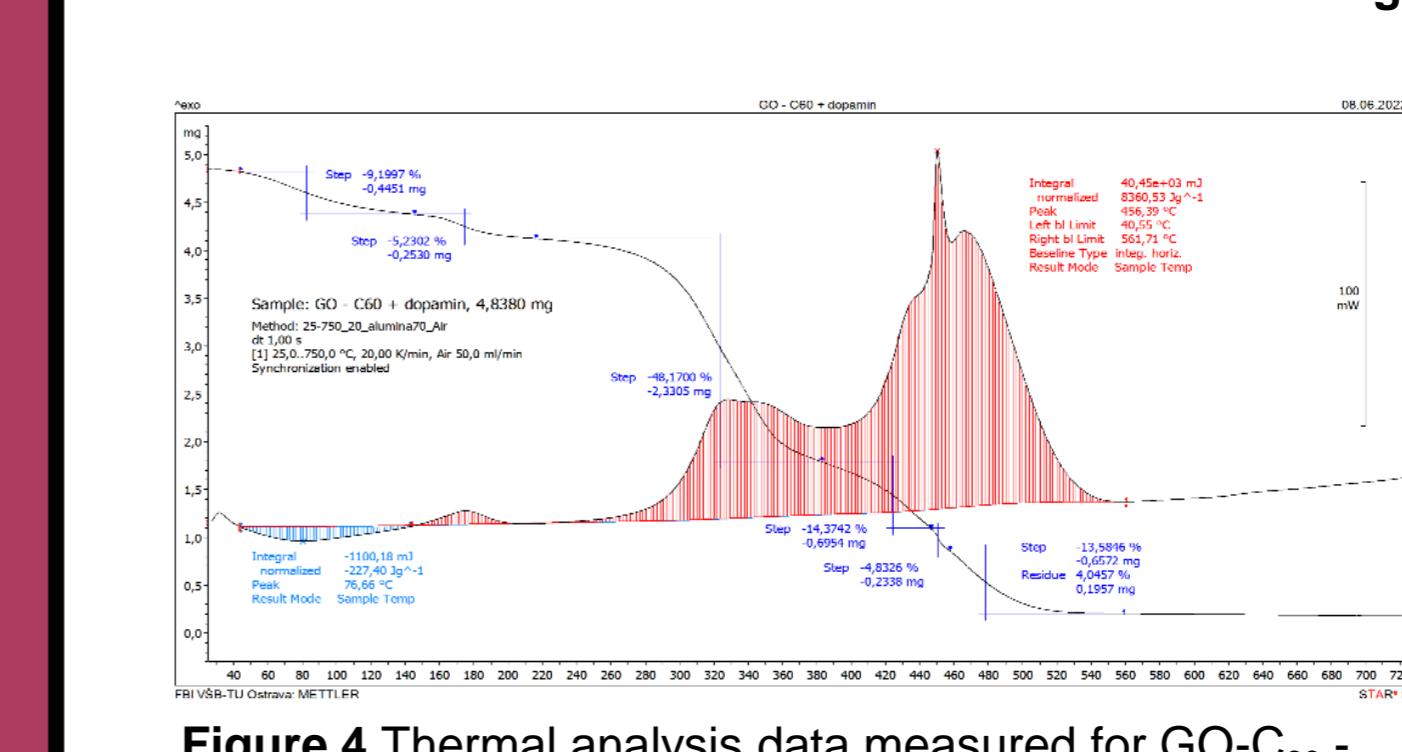


Figure 4 Thermal analysis data measured for GO-C<sub>60</sub>-PDA (TGA/DSC curves)

## CONCLUSIONS

The FTIR spectrum of GO contains well-resolved bands, which correspond to vibrations of individual types of bonds in the compound. The spectrum of GO-PDA is quite different. It is formed by broad bands that overlap. These bands correspond to different bond types and oxidation states, different cyclic structures (both heterocyclic and aromatic), and to a variety of bridging bonds and positions. The reason is the PDA structure. The PDA polymer consists of several various monomer units, which are diversely grouped and interconnected and are in different oxidation states. The results of the GO thermal analysis are consistent with those obtained by other research teams. The curves suggest that the reaction with DA resulted in a significant reduction of the epoxy bonds (C-O-C) present in both the initial GO and GO-C<sub>60</sub>. The PDA covering also increased thermal stability of both the initial materials. The PDA covering resulted in a change of the surface morphology. As reported by Bogdan et al., the PDA coating is always made up of two components. The first is a quasi-flat film with intrinsic roughness in the order of 1 nm. The second consists of PDA aggregates lying on top of this film. Larger aggregates can be easily separated by sonication. Therefore sonication may be used to achieve a more even covering and to reduce roughness. Since the GO used in our experiments was not sonicated, we assume that this fact may have influenced the newly formed surface structures. Different monomer units or PDAs could have intercalated between the oxidized carbon layers of the initial graphite. As reported by previous research, thickness of the PDA layer can be influenced by reaction conditions (reaction time, temperature, pH). For example, Jia et al. reported that the PDA layer may be up to 50 nm thick. Bogdan et al. therefore suggest that morphological characteristics of PDA coverings should be evaluated based on an agreed standardized protocol. Based on the results of the performed experiments, we assume that the coverings of GO and of the hybrid compound GO-C<sub>60</sub> changed their sorption properties. The introduction of novel functional groups will allow the formation of new non-covalent bonds with the surface of materials. Therefore the simultaneous use of initial materials and materials with a modified surface could expand the application potential of GO and its reduced forms.

## REFERENCES:

- LIEBSCHER, J. Chemistry of Polydopamine - Scope, Variation, and Limitation. *Eur. J. Org. Chem.* 2019, 31-32, 4976-4994. DOI: 10.1002/ejoc.201900445.
- BALL, V. Polydopamine Nanomaterials: Recent Advances in Synthesis Methods and Applications. *Front. Bioeng. Biotechnol.* 2018, 6, 109. DOI: 10.3389/fbioe.2018.00109.
- DELPARASTAN, P., MALOLARI, K., GAEHSIN, L., MESSERSMITH, P. B. Direct Evidence for the Polymeric Nature of Polydopamine. *Angew. Chem. Int. Ed. Engl.* 2019, 58, 4, 1077 – 1082. DOI: 10.1002/anie.201811763.
- PETRONE, L., KUMAR A., SUTANTO C., PATIL N. J., KANNAN S., et al. Mussel adhesion is dictated by time-regulated secretion and molecular conformation of mussel adhesive proteins. *Nature Communications*, 2015, 6, 8737. DOI: 10.1038/ncomms9737.
- KORD-FOROOOSHANI, P., POLEGA, E., THOMSON, K., BHUIYAN, MD. S. A., PINNARATIP, R., TROUGHT, M., KENDRICK, C., GAO, Y., PERRINE, K. A., PAN, L., LEE, B. P. Antibacterial Properties of Mussel-Inspired Polydopamine Coatings Prepared by a Simple Two-Step Shaking-Assisted Method. *Frontiers in Chemistry*, 2019, 7, 631. DOI: 10.3389/fchem.2019.00631.
- LI, H., XI, J., DONAGHUE, A. G., KEUM, J., ZHAO, Y., AN, K., MCKENZIE, E. R., FEI, R. Synthesis and catalytic performance of polydopamine supported metal nanoparticles. *Scientific Reports*, 2020, 10, 10416. DOI: 10.1038/s41598-020-67458-9.
- HUANG, X., QIAO K., LI, L., LIU, G., XU, X., LU, R., GAO, H., XU, D. Preparation of a magnetic graphene/polydopamine nanocomposite for magnetic dispersive solid-phase extraction of benzoylurea insecticides in environmental water samples. *Scientific Reports*, 2019, 9. DOI: 10.1038/s41598-019-45186-z.

## ACKNOWLEDGEMENTS

Autors thanks to P. Gemenier for FT-IR spectra. The publication was written within the project of Norway grants "Innovative carbon-based sorbents as an efficient way

3213200008.